

# Technical Data Sheet

## Black Ultra™ Proppants

### Description

Black Ultra™ proppants are available in 16/30, 20/40, 30/50 and 40/70 mesh sizes. These resin coated proppants utilize an advanced resin system, which bonds at low temperatures without the use of a consolidation aid for proppant flowback control.

### Typical Applications

Fracture treatments:

At closure stress up to:

- 8,000 psi [55 MPa] (16/30 and 20/40)
- 10,000 psi [69 MPa] (30/50 and 40/70)

At bottom-hole static temperatures\* from:

- 90 - 450°F [32 - 232°C]

\*Does not require low temperature consolidation aid down to recommended temperatures.

### Technical Advantages and Benefits

- Proppant flowback control in low temperature reservoirs without a consolidation aid
- High conductivity
- Proppant fines reduction
- Cyclic stress resistance
- Minimizes proppant embedment
- Reduces respirable silica dust exposure below PEL limits

### Typical Properties

---

Black Ultra™ Proppants  
<https://hexioninternet-hexioninternet-slave.azurewebsites.net/en-US/product/black-ultra>

Generated: July 1, 2022  
Issue Date:  
Revision: 11/8/2018 12:00:00 AM

© and ™ Licensed trademarks of Hexion Inc.

The information provided herein was believed by Hexion Inc. ("Hexion") to be accurate at the time of preparation or prepared from sources believed to be reliable, but it is the responsibility of the user to investigate and understand other pertinent sources of information, to comply with all laws and procedures applicable to the safe handling and use of the product and to determine the suitability of the product for its intended use. All products supplied by Hexion are subject to Hexion's terms and conditions of sale. **HEXION MAKES NO WARRANTY, EXPRESS OR IMPLIED, CONCERNING THE PRODUCT OR THE MERCHANTABILITY OR FITNESS THEREOF FOR ANY PURPOSE OR CONCERNING THE ACCURACY OF ANY INFORMATION PROVIDED BY HEXION**, except that the product shall conform to Hexion's specifications. Nothing contained herein constitutes an offer for the sale of any product.

Property	Value	Unit
Specific Volume	0.386 [0.0463], 0.383 [0.0439], 0.386 [0.0463], 0.385 [0.0461]	cm <sup>3</sup> /g [gal/lb]
API Mesh Size	16/30, 20/40, 30/50, 40/70	
Bulk Density	1.46 [12.2], 1.53 [12.8], 1.48 [12.4], 1.47 [12.3]	g/cm <sup>3</sup> [lb/gal]
Color	tan to reddish tan	
Composition	resin coated, northern white frac sand	
Median Particle Diameter	0.7660, 0.5775, 0.3825	mm
Particle Size Distribution	meets or exceeds API RP 19C	
Physical State	solid granule	
Pipe Fill Factor	0.685 [0.0821], 0.654 [0.0784], 0.676 [0.0810], 0.681 [0.0816]	cm <sup>3</sup> /g [gal/lb]
Resin Type	thermosetting, curable	
Solubility in Water, Brine & HCl	0.0	weight %
Specific gravity	2.59, 2.61, 2.59, 2.60	
Turbidity	≤ 250	NTU (FTU)

## Technical Considerations

- Grain-to-grain contact must occur and closure stress must be applied during the cure period for proper bonding
- Consolidation of curable product at bottom-hole static temperatures below 90°F [32°C] is achieved by use of Hexion's AcTivator™ low temperature consolidation aid


## Conductivity

PropTester, Inc. Long-Term Baseline Procedure

Proppant Concentration: 2 lb<sub>m</sub>/ft<sup>2</sup> [9.8 kg/m<sup>2</sup>], Temp: 150°F [66°C]

Closure Stress, psi [MPa]	2,000 [14]	4,000 [28]	6,000 [41]	8,000 [55]	10,000 [69]
---------------------------	------------	------------	------------	------------	-------------

Size	Conductivity (md-ft)				
16/30	7,841	6,575	3,697	1,189	615
20/40	5,449	3,941	2,811	1,109	637
30/50	2,315	1,778	1,185	779	346
40/70	1,227	1,107	704	383	252

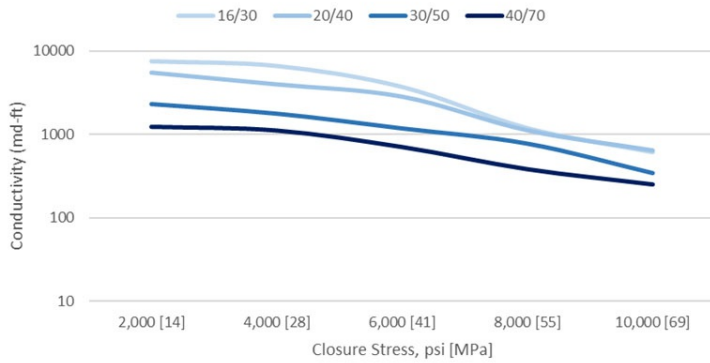


## Permeability

PropTester, Inc. Long-Term Baseline Procedure

Proppant Concentration: 2 lb<sub>m</sub>/ft<sup>2</sup> [9.8 kg/m<sup>2</sup>], Temp: 150°F [66°C]

Closure Stress, psi [MPa]	2,000 [14]	4,000 [28]	6,000 [41]	8,000 [55]	10,000 [69]
---------------------------	------------	------------	------------	------------	-------------

Size	Permeability (Darcy)				
16/30	365	333	195	67	36
20/40	260	192	142	59	35
30/50	116	90	62	42	20
40/70	59	54	36	20	14

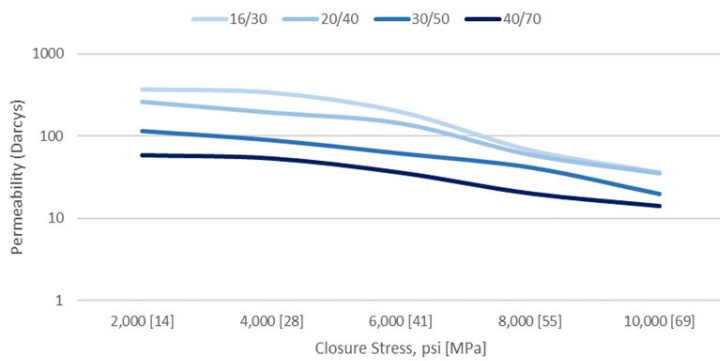

## Contact Information

Hexion  
Oilfield Technology Group  
15366 Park Row  
Houston, Texas 77084 USA  
+1 281 646 2800  
[www.hexion.com/oilfield](http://www.hexion.com/oilfield)

Customer Service  
+1 800 626 2116  
[otg.customerservice@hexion.com](mailto:otg.customerservice@hexion.com)

Technical Inquiries  
[otg.customerservice@hexion.com](mailto:otg.customerservice@hexion.com)

Black Ultra™ Proppants  
<https://hexioninternet-hexioninternet-slave.azurewebsites.net/en-US/product/black-ultra>

Generated: July 1, 2022  
Issue Date:  
Revision: 11/8/2018 12:00:00 AM

© and ™ Licensed trademarks of Hexion Inc.

The information provided herein was believed by Hexion Inc. ("Hexion") to be accurate at the time of preparation or prepared from sources believed to be reliable, but it is the responsibility of the user to investigate and understand other pertinent sources of information, to comply with all laws and procedures applicable to the safe handling and use of the product and to determine the suitability of the product for its intended use. All products supplied by Hexion are subject to Hexion's terms and conditions of sale. **HEXION MAKES NO WARRANTY, EXPRESS OR IMPLIED, CONCERNING THE PRODUCT OR THE MERCHANTABILITY OR FITNESS THEREOF FOR ANY PURPOSE OR CONCERNING THE ACCURACY OF ANY INFORMATION PROVIDED BY HEXION**, except that the product shall conform to Hexion's specifications. Nothing contained herein constitutes an offer for the sale of any product.